arXiv:1301.5124v1 [cond-mat.str-el] 22 Jan 2013

Stripe disorder and dynamics in the hole-doped antiferromagnetic insulator $La_{5/3}Sr_{1/3}CoO_4$

T. Lancaster,[1] S.R Giblin,[2] G. Allodi,[3] S. Bordignon,[3] M. Mazzani,[3] R. De Renzi,[3] P.G. Freeman,[4,5,*] P.J. Baker,[6] F.L. Pratt,[6] P. Babkevich,[7,*] S.J. Blundell,[7] A.T. Boothroyd,[7] J.S. Möller,[7] and D. Prabhakaran[7]

[1] *Centre for Materials Physics, Durham University,*
South Road, Durham, DH1 3LE, United Kingdom
[2] *School of Physics and Astronomy, Cardiff University,*
Queen's Buildings, The Parade, Cardiff, CF24 3AA, United Kingdom
[3] *Dipartimento di Fisica e Scienze della Terra, Università degli Studi di Parma, Viale G. Usberti 7A, I-43100 Parma, Italy*
[4] *Helmholtz-Zentrum Berlin fr Materialien und Energie,*
Hahn-Mietner-Platz 1, DE-14109 Berlin, Germany
[5] *Institut Laue-Langevin, BP 156, 38042 Grenoble Cedex 9, France*
[6] *ISIS Facility, Rutherford Appleton Laboratory, Chilton, Oxfordshire OX11 0QX, UK*
[7] *Oxford University Department of Physics, Clarendon Laboratory,*
Parks Road, Oxford, OX1 3PU, United Kingdom

(Dated: January 23, 2013)

We report on an investigation into the dynamics of the stripe phase of $La_{5/3}Sr_{1/3}CoO_4$, a material recently shown to have an hour-glass magnetic excitation spectrum. A combination of magnetic susceptibility, muon-spin relaxation and nuclear magnetic resonance measurements strongly suggest that the physics is determined by a disordered configuration of charge and spin stripes whose frustrated magnetic degrees of freedom are strongly dynamic at high temperature and which freeze out in a glassy manner as the temperature is lowered. Our results broadly confirm a recent theoretical prediction, but show that the charge quenching remains incomplete well below the charge ordering temperature and reveal, in detail, the manner in which the magnetic degrees of freedom are frozen.

PACS numbers: 75.47.Lx, 75.50.Lk, 76.75.+i, 74.62.En

The hour-glass spectrum of spin excitations observed using inelastic neutron scattering (INS) in the cuprate superconductors [1–13] has been linked to the occurrence of alternating patterns of spin and charge stripes in the copper oxide planes [14]. Although many cuprates exhibit hour-glass dispersion and show no evidence for stripe order, the recent discovery of such an excitation spectrum in stripe-ordered cobaltate materials provides compelling evidence that the hour-glass dispersion results from stripes [15]. The main features of the hour-glass spectrum can be reproduced by the spin-wave spectrum of perfectly ordered, weakly coupled antifrromagnetic (AFM) stripes [Fig. 1(a)] with phenomenological broadening [15]. Recently, however, a more detailed agreement has been obtained by a spin-wave calculation based on a stripe model that explicitly incorporates quenched disorder in the charge degrees of freedom and whose magnetic moments, through frustration, may be described in terms of cluster-glass behaviour at low temperature [16].

The wider implications of the link between stripes and hour-glass dispersion, on the cuprates in particular, has motivated this investigation into a hitherto unexplored aspect of the stripe phase dynamics in $La_{5/3}Sr_{1/3}CoO_4$. The study of very low-frequency excitations related to stripes, such as their slow collective motion, is outside the scope of inelastic neutron scattering. We have therefore selected muon-spin relaxation (μ^+SR) and nuclear magnetic resonance (NMR) as probes of this behavior. We note that, in contrast to muon and NMR spectroscopy, INS is insensitive to fluctuations on timescales much slower than $\hbar/\Delta E \approx 10^{-11}$s (where $\Delta E \approx 1$ meV is the energy scale of the resolution of the measurement) and so fluctuations on timescales longer than this will appear static to neutrons. Neutrons therefore take a "snap-shot" of the behaviour compared to μ^+SR and NMR measurements whose characteristic time scale is set, respectively, by the muon gyromagnetic ratio ($\gamma_\mu = 2\pi \times 135.5$ MHz T^{-1}) and on those of the nuclei being interrogated. In this paper we show that μ^+SR and NMR find dynamics and freezing of disordered moments which is consistent with a picture of disordered stripes whose dynamics are frozen out as the temperature is lowered.

The $La_{2-x}Sr_xCoO_4$ system is isostructural to the '214' family of cuprates, which includes $La_{2-x}Sr_xCuO_4$ and is based around well isolated, square layers of CoO_2. In the parent ($x = 0$) compound, commensurate AFM order is observed below $T = 275$ K [17]. Hole doping of the material involves exchanging Sr for La, resulting in the donation of positive charges to the CoO layers. For a doping of $x > 0.3$, magnetic order is modulated at 45° to the CoO bonds which is attributable to the self-organization of holes into arrays of charged stripes, which creates antiphase domain walls in the antiferromagnetic order [18]. The stripe order in $La_{5/3}Sr_{1/3}CoO_4$ involves diagonal lines of non-magnetic $S = 0$ Co^{3+} ions separated by bands of antiferromagnetically aligned Co^{2+} $S = 3/2$ ions, with intra- (J) and inter-stripe (J') antiferromagnetic exchange couplings as shown in Fig. 1(a).

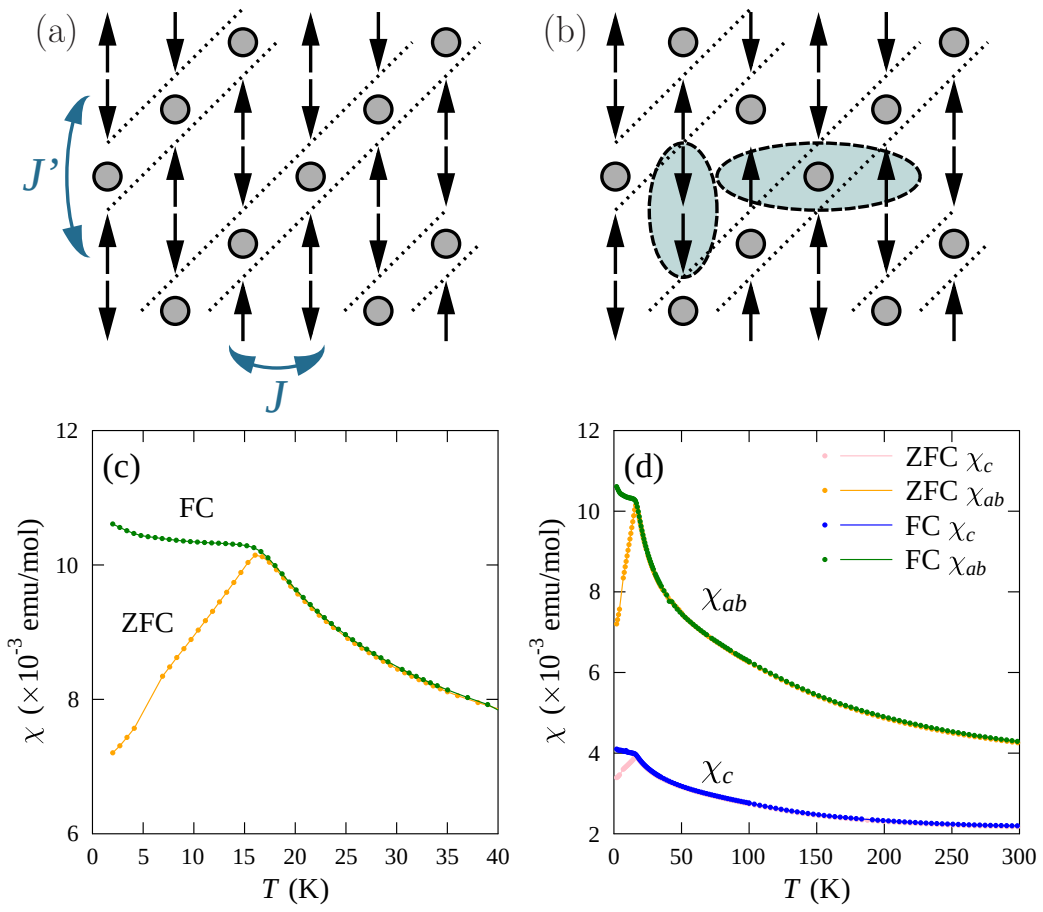

FIG. 1: (a) Perfect stripe order in the CoO_2 planes. (Circles represent non-magnetic Co^{3+}, arrows represent $S = 3/2$ Co^{2+} spins). (b) Disordering the charges leads to unfavorable exchange interactions between spins (shaded). (c) and (d) Magnetic susceptibility as a function of temperature for field cooled and zero-field cooled protocols for two crystal orientations.

It is currently assumed that the charge ordering of the Co ions sets in at a temperature $T_{\rm CO}$ well above room temperature, while magnetic Bragg peaks are observed in neutron diffraction below ~ 100 K [19]. The correlation lengths of the magnetic order were estimated to be $\xi = 10$ Å parallel to the stripes, and $\xi = 6.5$ Å perpendicular to the stripes [15].

Disordered stripes may be achieved by rearranging the charges or the spins of the configuration shown in Fig 1(a). Imperfections in the charge order are expected to be static at temperatures which are low in comparison to $T_{\rm CO}$ owing to the insulating nature of the material, while dynamic fluctuations should be expected in the spin degrees of freedom below room temperature. As shown in Fig 1(b), the introduction of charge disorder frustrates the antiferromagnetic coupling between spins, and this is the origin of the proposed cluster-glass behavior in this system [16].

To probe the slow dynamics of both charge and magnetic degrees of freedom, NMR measurements were made on a single crystal sample of $La_{5/3}Sr_{1/3}CoO_4$ in external fields $6 \leq B_{\rm app} \leq 9$ T applied in the ab plane. We expect that only ^{59}Co nuclei in spinless Co^{3+} ions will be detected, since for a magnetic Co^{2+} ion, the ^{59}Co nucleus experiences an instantaneous hyperfine field of order 10 T$\mu_{\rm B}^{-1}$, [22] whose fluctuations lead to very fast nuclear relaxation. The spectra were measured either by sweeping the field at a constant frequency ($T < 100$ K), or in frequency-sweep mode at fixed field ($T > 77$ K).

Example frequency-swept spectra from two probe nuclei: ^{139}La and ^{59}Co, measured in an external field $B_{\rm app} = 8$ T, are shown in Fig. 2(a-b). At room temperature, the ^{59}Co spectrum consists of a well-resolved line septet, originating from the nuclear $I = 7/2$ spin, split by the quadrupole coupling with the local electric field gradient (EFG). The central line, unperturbed to first order by the EFG, exhibits a sizeable shift with respect to the ^{59}Co reference [Fig. 2(d)]. The hyperfine coupling of ^{59}Co is estimated as ≈ 5 T from the comparison of the shift with the susceptibility χ_{ab} (see below and Fig. 1), and is compatible with the small transferred hyperfine field expected from the low-spin $S = 0$ state of Co^{3+}, confirming the localization of holes in the layers. The ^{139}La ($I = 7/2$) signal shows similar quadrupolar patterns, with higher-order satellites smeared out by EFG inhomogeneities which are larger at the La site. The central line is split into a doublet by magnetic interactions resulting from the occupancy of the nearest neighbor Co site by high-spin Co^{2+} or spinless Co^{3+}. The majority ^{139}La peak exhibits larger and temperature-dependent shifts, while the smaller shift of the minority peak is nearly temperature-independent [Fig. 2(c)].

Upon cooling below room temperature, the spectra are seen to broaden more than accounted for by demagnetization fields below 120 K, most dramatically seen in the ^{59}Co signal which shows a broad shoulder superimposed on the quadrupole septet at 100 K [Fig. 2(b)]. Such an excess of broadening reflects the onset of significant magnetic correlations below approximately the same temperature as the onset of magnetic Bragg peaks in neutron scattering [19]. It is likely that the static order here is short-ranged and results from the large applied field $B_{\rm app}$. Line broadening continues on cooling without abrupt changes with almost featureless spectra observed for $T < 10$ K [Fig. 2 (insets)].

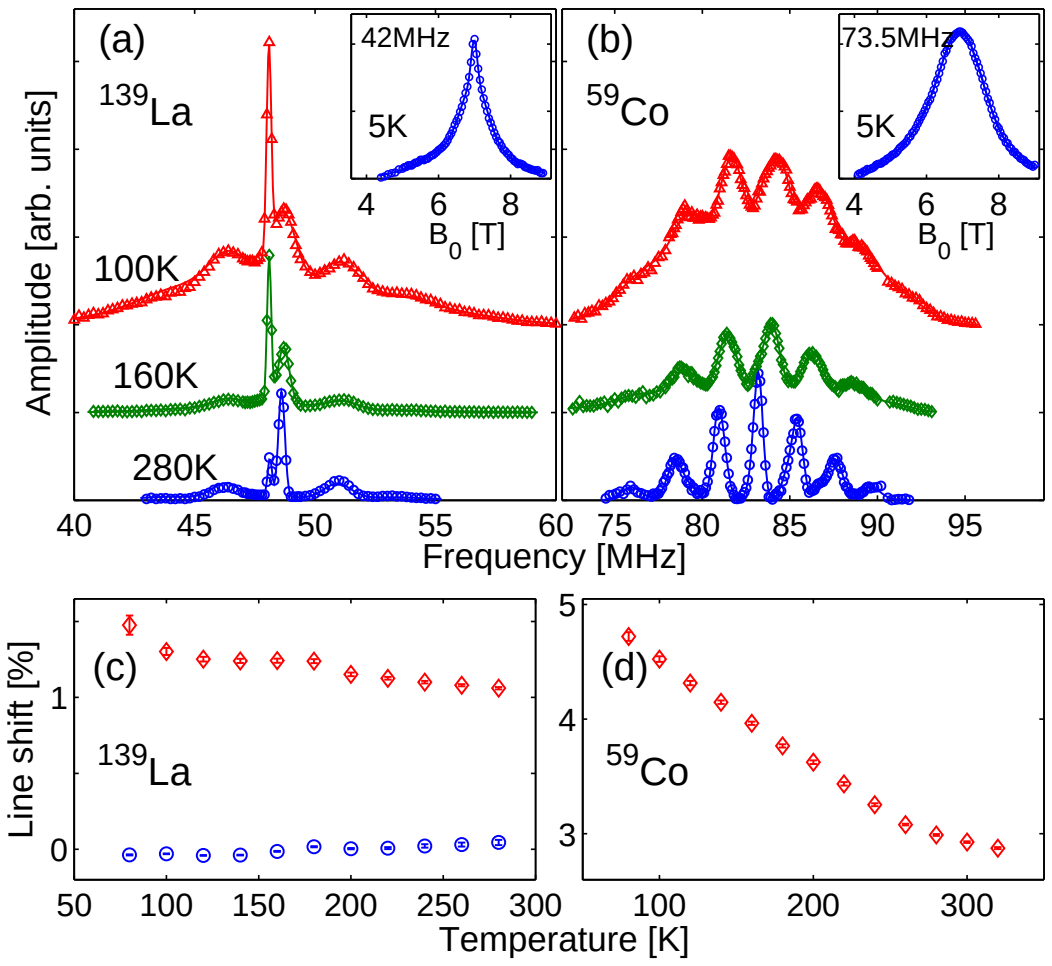

FIG. 2: (Color online) Top: frequency-swept (a) ^{139}La and (b) ^{59}Co NMR spectra in $B_{\rm app} = 8$ T at three selected temperatures. Insets: field swept spectra at 5 K. Bottom: shifts of (c) the central doublet of ^{139}La, and (d) the central line of ^{59}Co as a function of temperature.

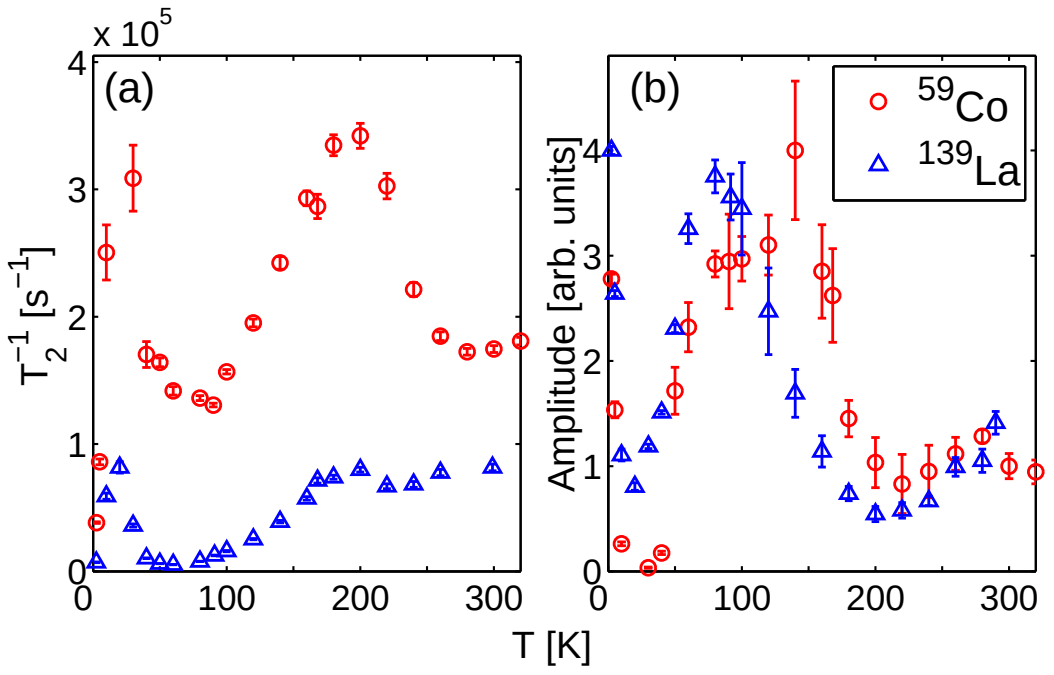

FIG. 3: (Color online) (a) Evolution of spin-spin relaxation rates T_2^{-1} with T for ^{59}Co (circles) and ^{139}La (triangles). (b) Integrated spectral amplitudes, corrected for the nuclear Boltzmann factor and T_2^{-1}, as a function of temperature.

The key result from our NMR is that the signal amplitude is partially lost (or wiped out) in two temperature intervals: above 100 K and, more severely, in the 10–40 K range. We note that the evolution of the measured spin-spin relaxation rates T_2^{-1} [Fig. 3(a)] exhibit two maxima: a broad peak round 200 K, and a sharper one at $T \approx 20$ K. However, when the integrated amplitudes of the two nuclei are corrected for T_2^{-1} [Fig. 3(b)] we find that the relaxation rates shown in Fig. 3(a) are actually those of a residual signal. Faster spin-spin relaxations manifest themselves as sizeable missing fractions (i.e. a signal wipeout), coinciding with the T_2^{-1} peaks. A wipeout of the signal is indicative of a broad distribution of relaxation rates, where signal components with T_2 much shorter than the instrumental dead time (≈ 10 μs) are lost, and correction of the slower-relaxing residual signal for T_2^{-1} does not recover the total amplitude.

Both wipeouts, which are indicative of very slow dynamical excitations, provide a strong indication of the physics of both the charge and spin degrees of freedom which are both relevant in describing stripe fluctuations. The two nuclear probes are both coupled to the EFG via their quadrupole moment as well as to the local magnetic field. The fast relaxations of ^{59}Co and ^{139}La above 100 K have no counterpart in our μSR data (described below), and therefore must be due to EFG fluctuations, to which $I = 1/2$ muons are not sensitive. The excitations underlying such EFG fluctuations most likely consists of thermally assisted hopping of holes across stripes, apparently taking place well below the charge ordering temperature. Such a charge motion slows down on cooling, down to a complete freezing at temperatures of the order of 100 K, at which the full NMR signal amplitude is recovered. The origin of the low temperature wipeout is almost certainly magnetic as shown by the magnetic measurements that we now describe.

Measurements of the DC magnetic susceptibility χ were made using a Quantum design MPMS, Fig. 1(c) and (d). No strong features are seen around 100 K [Fig. 1(d)] where magnetic Bragg peaks start to appear in neutron diffraction. The magnetic susceptibilities measured after zero-field (ZF) cooling and field cooling protocols (using a measuring field of $B = 100$ mT) show a gradual increase upon cooling before splitting below a temperature $T_{\mathrm{SF}} = 17$ K [Fig 1(c)]. This splitting is typical of a freezing of the magnetic moments at low temperature and reflects the fact that, after cooling in ZF to a region where the spins are statically frozen, we obtain a configuration which is less susceptible to magnetization than occurs if the frozen state is achieved in an applied field. AC susceptibility measurements were attempted on this system but a response could not be resolved.

μ^+SR measurements [20] were made at the ISIS Facility using the EMU spectrometer and at the Swiss Muon Source (SμS) using the DOLLY and GPS spectrometers. The initial muon spin was directed along the c-axis of the material, so that the muon spins are initially perpendicular to the CoO$_2$ layers. Example μ^+SR spectra measured in zero applied magnetic field at SμS are shown in Fig. 4(a). A heavily damped oscillation in the asymmetry is observed at 5 K. These oscillations are characteristic of a quasi-static local magnetic field at the muon stopping site, which causes a coherent precession of the spins of those muons with a component of their spin polarization perpendicular to this local field. The frequency of the oscillations is given by $\nu_i = \gamma_\mu B_i/2\pi$, where B_i is the average magnitude of the local magnetic field at the ith muon site. Any fluctuation in magnitude of these local fields will result in a relaxation of the oscillating signal. On increasing the temperature the frequency of the oscillations falls slowly [Fig. 4(b)] but the amplitude of the oscillation drops very rapidly [Fig. 4(c)] until only a residual, broad feature is observed for temperatures $20 \lesssim T \lesssim 30$ K.

In order to follow the slow dynamics in this system complementary μ^+SR data were measured over a longer time window at the ISIS facility, where the limited time resolution does not allow us to resolve oscillations or relaxation rates $\gtrsim 10$ MHz. Instead, we see a decrease in the relaxing amplitude A_{rel} as the material is cooled below 40 K. This is because the local field in the ordered state strongly depolarizes the muon spin if local field components are perpendicular to the initial muon-spin polarization (or have no effect on it if local field components are parallel to the initial muon-spin polarization), removing the relaxing asymmetry from the spectrum. Example spectra measured at ISIS are shown in Fig. 4(d). In view of the limitations caused by the ISIS time resolution, we parametrize the data with a stretched exponential function

$$A(t) = A_{\mathrm{rel}} e^{-(\lambda t)^{\beta}} + A_{\mathrm{bg}} \qquad (1)$$

where A_{bg} is a background contribution accounting for those muons which stop in the sample holder or cryostat

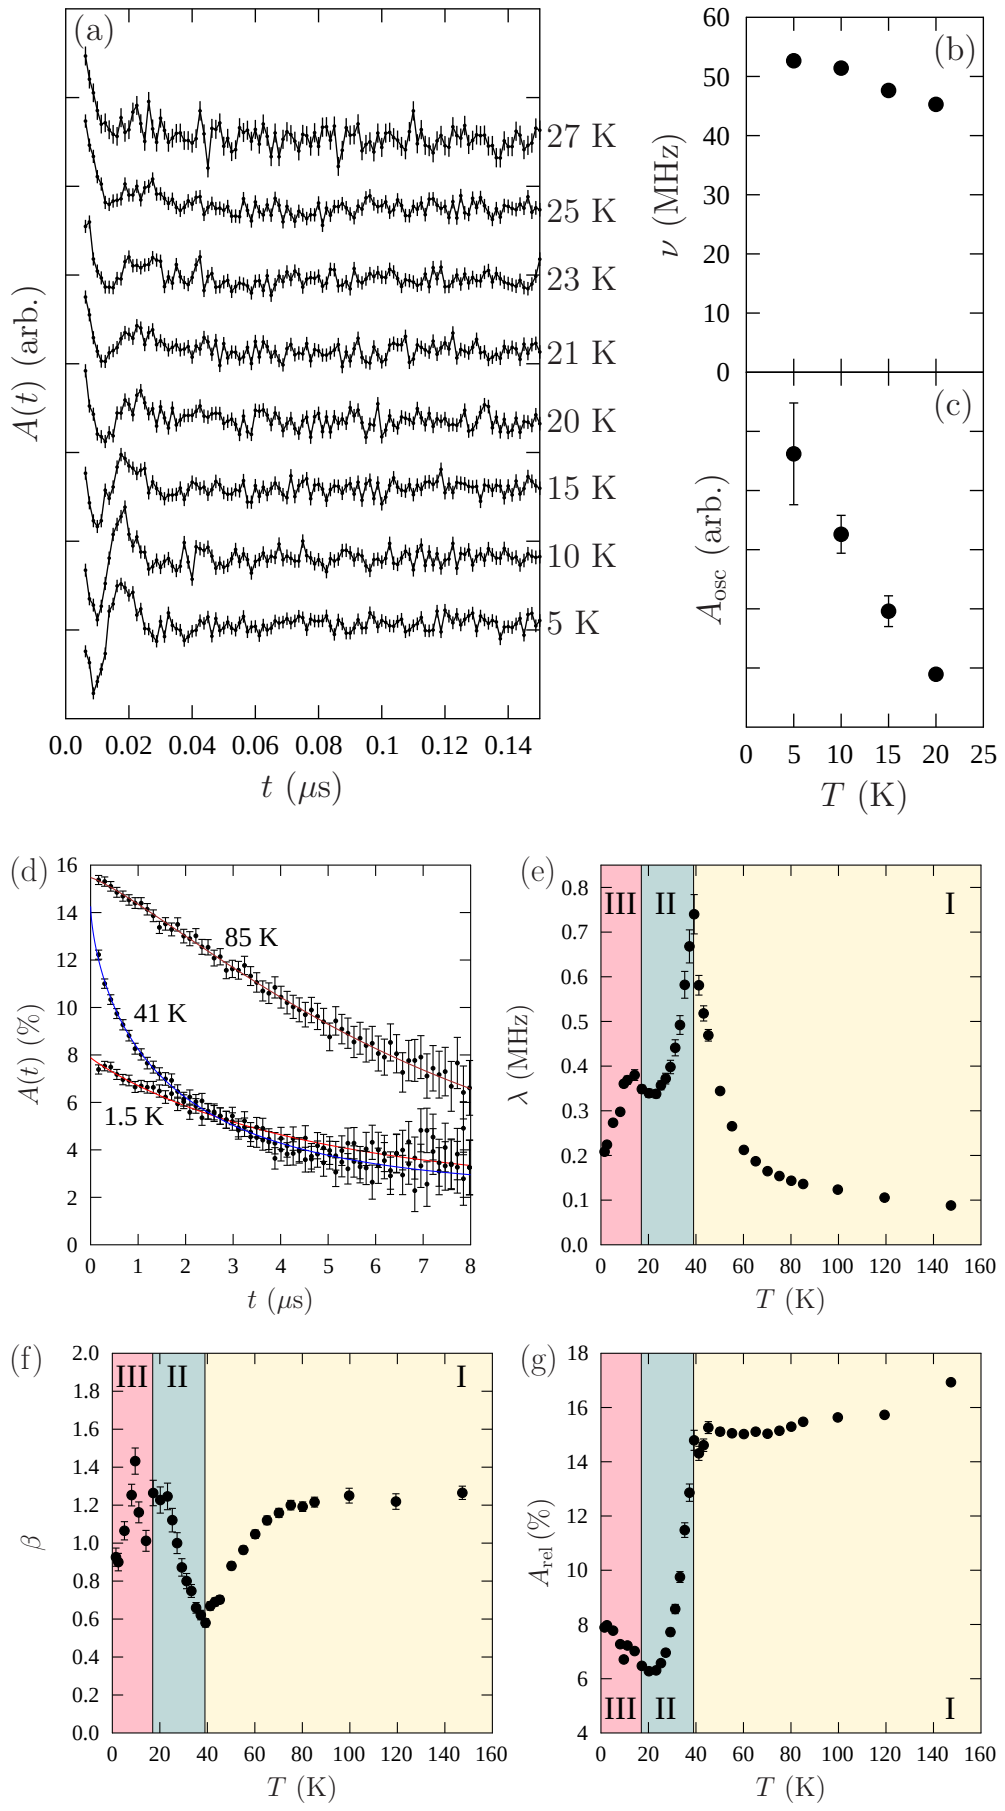

FIG. 4: (a) Low-temperature ZF spectra measured at SμS. Evolution of (b) the frequency ν and (c) the amplitude of the oscillating signal with temperature. (d) Example ZF spectra measured at ISIS. Temperature evolution of the parameters in Eq. 1: (e) relaxation rate λ; (f) stretching parameter β (g) relaxing amplitude $A_{\rm rel}$.

tail. We expect that the muon relaxation rate is determined by the relation $\lambda \propto \Delta^2\tau$, where $\Delta^2 = \gamma_\mu^2\langle B_i^2\rangle$ and τ is the correlation time.

Again we note that no features are observed around 100 K, where magnetic Bragg peaks become resolvable. Three regions in temperature are apparent in the behavior of the relaxing amplitude $A_{\rm rel}$, the relaxation rate λ and the stretching factor β. On cooling in region I ($T > 40$ K) the relaxation rate λ increases slowly, with the increase becoming more dramatic below ≈ 70 K before peaking sharply at $T = 39$ K. The stretching parameter β also begins to drop below ≈ 70 K from a high temperature value of $\beta = 1.2$ to a minimum of $\beta \approx 0.5$ at 39 K. The relaxing amplitude $A_{\rm rel}$ falls slowly across region I. On entering region II ($25 \lesssim T \leq 39$ K) $A_{\rm rel}$ drops rapidly, β increases towards its high temperature value and λ decreases. Finally, in region III ($T \lesssim 20$ K) β is difficult to fit and shows some scatter, $A_{\rm rel}$ increases and there is another peak in λ centred around 15 K.

Taken with the magnetic susceptibility and NMR these μ^+SR results allow an insight into the behavior of the stripes in $\rm La_{5/3}Sr_{1/3}CoO_4$. The snap-shot taken by neutron diffraction indicates that ordered stripes have formed at temperatures below 100 K and the μ^+SR suggests that at these high temperatures (in region I) spins within the stripes are rapidly fluctuating on the muon time scale. A decrease in temperature causes these fluctuations to slow down, increasing τ and hence λ. The crossover around $T = 39$ K marks the point where spins begin to lock together, that is, they suddenly become well correlated on the muon time-scale. It may be that this results from the stripes of spins within each $\rm CoO_2$ layer becoming well correlated at this temperature, while interlayer correlations remain small; it may also reflect three-dimensional clusters of spins becoming correlated. These increased correlations produce a sizeable increase in Δ which causes the muon asymmetry to be rapidly depolarized, leading to a drop in $A_{\rm rel}$. Dynamics in this region both preclude a μ^+SR precession signal and lead to the low-temperature NMR wipeout. As the system is cooled through the 40–20 K region, relaxation channels gradually freeze out leading to longer τ and resulting in a λ too fast to resolve, which causes the gradual decrease in $A_{\rm rel}$. Finally, the peak in λ at 15 K and increase in $A_{\rm rel}$ below 20 K, and a crossover to a more static configuration, points to the dynamics of the clusters freezing out below 20 K. This freezing explains (1) the μ^+SR precession signal, (2) the splitting of the ZFC and FC χ data and (3) the reappearance of the NMR signal.

Further evidence for this picture comes from μ^+SR measurements made in applied longitudinal magnetic field (with the field directed along c). In such measurements the applied field acts to lock a fraction of the muons along the z-direction, reducing the extent of the relaxation caused by the fluctuating internal field at the muon site. In region I the application of a field causes little change in the relaxation rate. In region III, modest fields change the relaxation considerably, typical of a static field configuration. Region II shows intermediate behavior. It is also worth noting the similarity between the μ^+SR results reported here and those of other frustrated systems (e.g. [21]) where the glassy dynamics freeze out gradually on cooling.

In conclusion, the stripes that dominate the low-energy physics of $\rm La_{5/3}Sr_{1/3}CoO_4$ show a gradual freezing out of spin dynamics upon cooling. This is suggestive of the glassy character of the dynamics, as predicted for the model of stripe dynamics based on magnetic frustration caused by quenched disorder in the charge sector. However the presence of a high temperature wipeout in the NMR, which has no analogue in μ^+SR, indicates that this charge quenching is not complete. The influence of such dynamics of stripe phases on the physics of the cuprates remains an open and intriguing question [16].

Part of this work was carried out at the SμS, Paul Scherrer Institut, Switzerland and at the STFC ISIS facility, UK and we are grateful for the provision of beamtime and to R. Schuermann and A. Amato for technical support. We thank EPSRC (UK) for financial support.

---

[*] Current address: Laboratory for Quantum Magnetism, Ecole Polytechnique Fdrale de Lausanne, CH-1015 Lausanne, Switzerland

[1] M. Arai, T. Nishijima, Y. Endoh, T Egami, S. Tajima, K. Tomimoto, Y. Shiohara, M. Takahashi, A. Garrett and S.M. Bennington, Phys. Rev. Lett. **83** 608 (1999).

[2] P. Bourges, Y. Sidis, H.F. Fong, L.P. Regnault, J. Bossy, A. Ivanov and B. Keimer, Science **288**, 1234 (2000).

[3] S.M. Hayden, H. A. Mook, P. Dai, T.G. Perring and F. Dogan, Nature **429**, 531 (2004).

[4] D. Reznik, P. Bourges, L. Pintschovius, Y. Endoh, Y. Sidis, T. Masui and S Tajima, Phys. Rev. Lett. **93**, 207003 (2004).

[5] C. Stock, W. J. L. Buyers, R. A. Cowley, P. S. Clegg, R. Coldea, C. D. Frost, R. Liang, D. Peets, D. Bonn, W. N. Hardy and R. J. Birgeneau, Phys Rev. B **71**, 024522 (2005).

[6] V. Hinkov, P. Bourges, S. Pailhes, Y. Sidis, A. Ivanov, C. D. Frost, T. G. Perring, C. T. Lin, D. P. Chen and B. Keimer, Nature Phys. **3**, 780 (2007).

[7] B. Fauqué, Y. Sidis, L. Capogna, A. Ivanov, K. Hradil, C. Ulrich, A. I. Rykov, B. Keimer and P. Bourges, Phys. Rev. B **76**, 214512 (2007).

[8] G. Xu, G. D. Gu, M. H ucker, B. Fauqué, T. G. Perring, L. P. Regnault and J. M. Tranquada Nature Phys. **5**, 642 (2009).

[9] N.B. Christensen, D. F. McMorrow, H. M. Rønnow, B. Lake, S. M. Hayden, G. Aeppli, T. G. Perring, M. Mangkorntong, M. Nohara, and H. Tagaki Phys. Rev. Lett. **93**, 147002 (2004).

[10] B. Vignolle, S. M. Hayden, D. F. McMorrow, H. M. Rønnow, B. Lake, C. D. Frost and T. G. Perring Nature Phys. **3**, 163 (2007).

[11] M. Matsuda, M. Fujita, S. Wakimoto, J. A. Fernandez-Baca, J. M. Tranquada and K. Yamada Phys. Rev. Lett. **101**, 197001 (2008).

[12] O. J. Lipscombe, B. Vignolle, T. G. Perring, C. D. Frost, and S. M. Hayden Phys. Rev. Lett. **102**, 167002 (2009).

[13] J.M. Tranquada, H. Woo, T. G. Perring, H. Goka, G. D. Gu, G. Xu, M. Fujita and K. Yamada Nature **429**, 534 (2004).

[14] J.M. Tranquada, Physica B **407**, 1771 (2012) and references therein.

[15] A.T. Boothroyd, P. Babkevich, D. Prabhakaran and P.G. Freeman, Nature **471**, 341 (2011).

[16] E.C. Andrade and M. Vojta, Phys. Rev. Lett. **109**, 147201 (2012).

[17] K. Yamada, M. Matsuda, Y. Endoh, B. Keimer, R. J. Birgeneau, S. Onodera, J. Mizusaki, T. Matsuura and G. Shirane Phys. Rev. B **39**, 2336 (1989).

[18] M. Cwik, M. Benomar, T. Finger, Y. Sidis, D. Senff, M. Reuther, T. Lorenz, and M. Braden, Phys. Rev. Lett. **102**, 057201 (2009).

[19] A.T. Boothroyd, P. Babkevich, D. Prabhakaran and P.G. Freeman, Nature **471**, 341 (2011), supplementary information.

[20] S.J. Blundell, Contemp. Phys. **40**, 175 (1999).

[21] T. Lancaster, S. J. Blundell, P. J. Baker, H. J. Lewtas, W. Hayes, F. L. Pratt, H. T. Yi, and S.-W. Cheong, Phys. Rev. B **80**, 020409R (2009).

[22] A. J. Freeman and R. E. Watson, *Hyperfine Interactions in Magnetic Materials*, in *Magnetism IIA*, eds. G. T. Rado, H. Suhl, Academic Press, New York (1965).